


trimal[®]-41

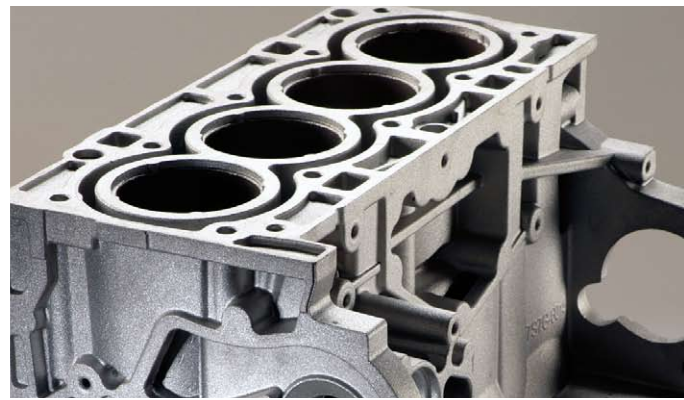

trimal[®]-41

High pressure die cast alloy
for applications under elevated
temperatures

trimet

trimal[®]-41

High pressure die cast alloy for applications under elevated temperatures

trimal[®]-41 (AlSi9Cu3ZnMg) alloy is a low iron die cast alloy that was developed for die cast parts requiring high static and dynamic properties, in particular at elevated temperatures. **trimal[®]-41** has excellent castability and allows for low-pore casting, even of parts with great differences in wall thicknesses.

The copper content of 3% makes the alloy heat resistant. Adding a zinc content of 2% enables the alloy to be hardened in eight days at room temperature. As a result, T5 heat treatment is not necessary but can be performed if desired.

The manganese content of 0.8% prevents sticking to the die and provides temperature stability at the same time. By adding strontium to **trimal[®]-41**, the silicon eutectic is modified, thus improving ductility. In addition, strontium creates a slight spheroidizing of the intermetallic phases. The copper content limits the corrosion resistance.

Chemical composition in weight%


%	Si	Fe	Cu	Mn	Mg	Zn	Ti	Other
Min.	6,0		2,0	0,6	0,10	0,5	0,03	
Max.	11,0	0,4	4,0	1,0	0,55	3,5	0,12	0,2

trimal[®]-41 is modified with strontium upon request.

Mechanical properties

The following mechanical properties were determined using real parts and are considered to be reference values for the use of the alloy.

Duration of hardening at RT in days

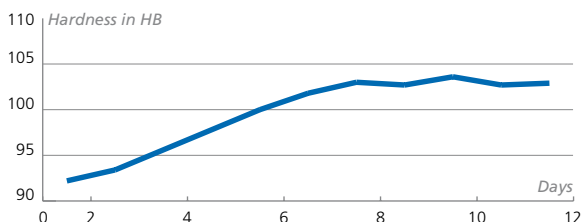

Temper	Yield Strength Rp0.2 N/mm ²	Tensile Strength Rm N/mm ²	Elongation A %	Hardness HB
F	>170	>240	1 - 5	90 - 110
T5	>180	>250	>1	95 - 115

Applications

trimal[®]-41 was developed specially for engine blocks. It is used mainly in applications such as engines or motor parts, casings or end plates that require great stability at, for example, elevated temperatures. The alloy can be used to cast complicated designs and very thin walls.

trimal[®]-41 is extremely machinable and weldable. It can be hard anodized to improve the tribologic properties.



Copyright

The information provided in this brochure was gathered in proper tests and is given to the best of our knowledge and belief. However, as with all application suggestions, they are solely nonbinding references that are not covered by our contractual obligations (including any third-party copyrights) and for which we are not liable. The data do not constitute a guarantee for properties and do not release the user from his responsibility to test whether our products are suited for their intended use. The reproduction, translation and copying of this brochure, in whole or part, are subject to our express authorization. New alloys and their technological advancements that are developed after the brochure has gone into print will be presented in the next issue.

trimet

TRIMET ALUMINIUM AG • Aluminiumallee 1 • D-45356 Essen
Tel. +49 201-3660 • www.trimet.de